

Leveraging transfer learning for accurate estimation of ionic migration barriers in solids

Reshma Devi¹, Keith T. Butler^{2,*}, and Gopalakrishnan Sai Gautam^{1,*}

¹Department of Materials Engineering, Indian Institute of Science, Bengaluru, 560012, India

²Department of Chemistry, University College London, London WC1E 6BT, United Kingdom

*Email: k.t.butler@ucl.ac.uk; saigautamg@iisc.ac.in

Abstract

Ionic mobility, which determines the rate performance of several applications, such as batteries, fuel cells, and electrochemical sensors, is exponentially dependent on the migration barrier (E_m) for ionic motion within solids, a quantity that is difficult to measure experimentally or estimate computationally. Previous approaches to identify materials with high ionic mobility have often relied on imprecise descriptors or rules-of-thumb given the lack of generalizable models to predict E_m swiftly and accurately. Here, we present a graph neural network based architecture that leverages principles of transfer learning to efficiently and accurately predict E_m across a diverse set of materials. We use a model (labeled MPT) that has been simultaneously pre-trained on seven distinct bulk properties, introduce modifications into the MPT model to build inductive bias on different migration pathways in a structure, and subsequently fine-tune (FT) on a manually-curated literature-derived dataset of 619 E_m data points calculated with density functional theory. Specifically, we propose four different architectural modifications of the MPT model that differ on the number of instances of the MPT model used, the structural images or bands taken as an input, and the presence/absence of attention layers. Importantly, our best-performing FT model (labeled MODEL-3) demonstrates substantial improvements in prediction accuracy compared to classical machine learning methods, graph models trained from scratch, and a universal machine learned interatomic potential, with a R^2 score of 0.703 and a mean absolute error of 0.261 eV on the test set. Notably, MODEL-3 is able to distinguish different migration pathways within a given structure and also demonstrates excellent ability to generalize across intercalant compositions and chemistries. As a classifier, MODEL-3 exhibits 80% accuracy and 82.8% precision in identifying materials that are ‘good’ ionic conductors (i.e., structures with $E_m < 0.65$ eV). Thus, our work demonstrates the effective use of FT strategies, architectural modifications necessary to learn a target property, and the adaptability of our MPT model, which can be extended to make predictions on other data-scarce material properties. Finally, the demonstrated abilities of MODEL-3 highlights its potential use in identifying materials with high ionic mobility with applications in batteries and beyond.

1 Introduction

Ionic conductivity (σ) or diffusivity (D) or mobility (μ) in a crystalline solid is an important material property that governs the rate performance of several applications, such as rechargeable batteries, fuel cells, and electrochemical sensors. In the case of secondary batteries, the core operating principle involves the reversible movement of mobile ions (such as Li^+ , Na^+ , K^+ , Mg^{2+} , or Ca^{2+}) between electrode materials that are typically intercalation compounds and across an electronically-insulating electrolyte, which facilitates electron exchange via the external circuit. [1] Thus, the rate performance of a given rechargeable battery is often limited by the ionic mobility of the electroactive ion in the intercalation electrode and/or in the solid electrolyte (in case of all-solid-state batteries). [2, 3] Thus, significant improvements in rate performance of batteries (and other electrochemical applications) can be effected by the use of novel materials [4] that exhibit high μ of the electroactive ion, indicating that computational or experimental screening strategies [5] need to predict $\mu/\sigma/D$ swiftly and accurately for the identification of candidate materials.

Mathematically, μ and σ are directly proportional to one another, with σ usually described by the Nernst-Einstein equation ($\sigma = \frac{q^2 x D(x)}{k_B T}$), where q , x , k_B , and T are the charge and concentration of the intercalant, the Boltzmann constant, and temperature, respectively. $D(x)$ relates the diffusive flux to the concentration gradient via Fick’s first law, [6] and can be expressed as $D(x) = D_J(x)\theta(x)$. D_J is the jump diffusion coefficient that captures the rate of atomic migrations and the correlations among atomic hops, and θ is the thermodynamic factor that accounts for any non-ideal interactions between the intercalant and the diffusion carrier (typically vacancies). Thus, macroscopic diffusion of ions in a solid (D) is directly related to microscopic atomic hops (D_J) that happen within the crystal structure. In the case of ideal interactions between the intercalant and vacancies, where each atomic hop exhibits an identical frequency (or probability) of occurrence, D simplifies to Equation 1.

$$D = f.g.a^2.\nu.\exp\left(-\frac{E_m}{k_B T}\right) \quad (1)$$

f is the correlation factor, g is the geometric factor that describes the diffusion channel connectivity, a is the hop distance, ν is the pre-factor that depends on vibrational frequencies of atoms, and E_m is the activation barrier associated with the atomic migration. Note that the x dependence of D can arise from x dependence of f , g , a , ν , and/or E_m . Importantly, E_m is the most dominant factor that determines D (and by extension σ/μ), given that it has an exponential influence on D , and hence becomes the most crucial quantity to calculate/measure for rate performance estimation in any application.

Considering reasonable battery performance metrics, such as charge/discharge at a rate of C/2 and an operating temperature of 300 K, the tolerable limit for E_m in electrodes lies between 525 meV for micron-sized particles and 650 meV for nano-sized particles. [7] Minimizing E_m is essential for high μ , prompting efforts to identify factors that lower E_m . Previously proposed design principles for selecting structures with high μ include avoiding preferred coordination environments, minimizing coordination number changes during migration, and maximizing volume per anion with non-close-packed structures. [7, 8] However, these principles are not universally applicable, especially for large intercalants, prompting Lu et al. [9] to refine the strategies for Ca^{2+} that emphasized optimal transition state geometry not containing face-sharing polyhedra and having higher degrees of freedom. Moreover, close-packed structures (i.e., structures without a high volume per anion) have also demonstrated high σ , as with the case of Mg^{2+} in spinel chalcogenides. [10–13] Other structural descriptors that have been identified to correlate with E_m in solids, such as spinels, garnets, and olivines, include migrating ion-anion distances, [14] and the ‘migration number’ [15] that encompasses

electronegativities, oxidation states, and ionic radii. Nevertheless, despite advancements in understanding factors that influence μ (or E_m) in specific systems, a generalized rule or model that is applicable across a wide variety of solid systems [16] remains elusive so far.

For models predicting E_m to be practically useful, the models have to make predictions that are as accurate as and are significantly faster than experimental measurements or computational techniques. Additionally, for constructing generalizable models for E_m predictions, a reliable dataset of measured or calculated E_m across a wide variety of systems is necessary. In terms of measuring E_m , direct experimental techniques such as electrochemical impedance spectroscopy (EIS [17, 18]), galvanostatic intermittent titration technique, [19–22] and nuclear magnetic resonance based methods [23–25] are typically used. However, these techniques can be resource-intensive and contain challenges, such as (lack of) sensitivity to the short time and length scales of ionic migration, dependence on sample preparation or measurement conditions, and specific equipment requirements (e.g., inert ion-blocking electrodes in EIS). Thus, generating E_m dataset(s) based solely on experimental measurements can be challenging and models that exhibit swift and accurate E_m predictions can certainly be used for targeted experimentation on select materials.

On the other hand, computational strategies to estimate E_m include bond valence (BV [26, 27]) analysis, density functional theory (DFT [28, 29]) based nudged elastic band (NEB [30, 31]) calculations and molecular dynamics (MD [32–34]) simulations, with each technique exhibiting its own advantages and challenges. For example, BV analysis is computationally efficient but is error-prone in estimating E_m due to its empirical nature involving static structures and ionic bond models. [35, 36] Ab initio MD simulations enable direct estimation of D but are computationally intractable for sampling dynamics in large systems and over nanosecond time scales, thereby limiting their accuracy. [37] While machine learned interatomic potentials (MLIPs [38–40]) can enable MD simulations to sample over larger length and longer time scales than ab initio MD, the potentials have to be nominally fine-tuned for specific chemistries for accurate D or E_m estimation, thus resulting in higher computational costs.

DFT-NEB calculations offer accurate and direct E_m estimation by modeling the the minimum energy path (MEP) of atomic migration using an elastic band of intermediate images connected by spring forces, which is subsequently relaxed using DFT. While the accuracy of DFT-NEB can depend on the selected exchange-correlation (XC) functional, the computational cost scales with system size, and convergence to the MEP can be problematic. [41] Efforts to accelerate NEB calculations include improved path initialization [42, 42] and quicker energy estimation using algorithms like ‘Pathfinder’ and ‘ApproxNeb’, [14, 43] with possible reductions in accuracy. Nevertheless, computationally demanding DFT-NEB calculations remain the state-of-the-art for accurate E_m estimations in solids, making the case for models that can accurately and swiftly predict E_m .

Machine learning (ML) models have been used in the recent past to understand trends in E_m in specific systems. For example, Jalem et al. [44] developed a neural network model with features from both DFT relaxed structures and literature to predict DFT-NEB calculated E_m across 72 olivine-based structures. Apart from identifying structural descriptors that primarily correlated with E_m , Jalem et al.’s model exhibited a validation R^2 score and root mean squared error (RMSE) of 0.978 and 0.0619 eV, respectively. As a follow-up work, Jalem and co-workers [45] used Bayesian optimization to identify compositions with low E_m (<0.3 eV) within the tavorite framework by training on 317 DFT-NEB calculated E_m , with the model exhibiting a $\sim 90\%$ success rate and some knowledge transfer from Li-based compositions to Na. Sendek et al. [46] used logistic regression on experimental σ data available on ~ 40 materials that were down-selected from a screening process beginning with 12,831 Li-containing compounds from the materials project (MP [47]) and reported

a X-randomization performance metric of 0.59 indicating statistical significance in predicting high σ . Kim et al. [48] investigated anti-perovskites as solid-state electrolytes by employing various ML-based regression models that were trained on ~ 608 DFT-NEB calculated E_m using 44 physical, chemical, electrical, and geometric descriptors, with their best model achieving a RMSE of 0.71 eV. A significant limitation of existing ML models is their poor generalizability due to their reliance on narrow training datasets focused on specific structures or chemistries, resulting in poor accuracy when tested out-of-domain.

An important challenge in developing ML models for materials science is the scarcity of data on critical material properties, such as E_m . For example, graph neural networks (GNNs) ideally require datasets with $\sim 10^4$ data points to perform optimally, [49] while typical material science datasets often contain only a few thousand or fewer data points. Transfer learning (TL), which involves pre-training (PT) a model on a larger (material property) dataset and subsequently fine-tuning (FT) on a smaller (target property) dataset, offers a promising solution to this data insufficiency. [50] Indeed, we have demonstrated in our previous work the effectiveness of various PT/FT strategies using the atomistic line graph neural network (ALIGNN [51]) as the base architecture, showing that FT models consistently outperform models trained from scratch (i.e., without any PT) across seven diverse bulk material properties. [52] Furthermore, we developed a multi-property pre-trained (MPT) model, which was trained simultaneously on all seven bulk material properties and exhibited better performance than pair-wise PT/FT models on a completely out-of-domain property on 2D materials. [52] Thus, principles of TL and our constructed MPT model can be leveraged for E_m predictions.

In this work, we use TL and our MPT framework to construct generalizable models for E_m predictions across a wide range of structural groups, compositions, chemistries, and migration pathways. We develop four different architectural modifications for FT the MPT model, by considering either the initial and final positions of the migrating ion or an interpolated band of images that represents the migration as inputs. Additionally, we explore the utility of adding attention layers to increase the model’s sensitivity to critical parameters that govern E_m . For training and testing, we employ a manually-curated DFT-NEB E_m data obtained from literature, developed as a parallel work. [53] Our dataset contains 619 distinct migration pathways that span 58 different space groups and diverse chemistries and compositions.

Notably, we observe our best-performing FT model, named ‘MODEL-3’, to exhibit R^2 scores and mean absolute errors (MAEs) of 0.703 and 0.261 eV, respectively, on the test set. MODEL-3 outperforms both scratch GNN and classical ensemble ML models, by at least 77.53% on test R^2 scores and 17.92-44.13% on test MAEs. Importantly, MODEL-3 displays the ability to generalize across different migration pathways, migrating ion compositions, and varying anion or transition metal chemistries within a structural framework. We find MODEL-3 to be more accurate (by 280% on test R^2 and 23.24% on test MAE) compared to E_m estimated by a universal MLIP, namely the multi atomic cluster expansion (MACE [54, 55]). Also, as a classifier, MODEL-3 achieves an 80% accuracy and an 82.8% precision in identifying ‘good’ conductors (i.e., structures with $E_m < 0.65$ eV). The FT model architectures developed in this work illustrate the adaptability of the MPT model to predict other data-scarce material properties. Finally, our best-performing model should be highly useful in rapidly identifying materials with good μ , which can be subsequently validated with DFT-NEB calculations or experiments, and eventually be used for batteries and other applications.

2 Data description

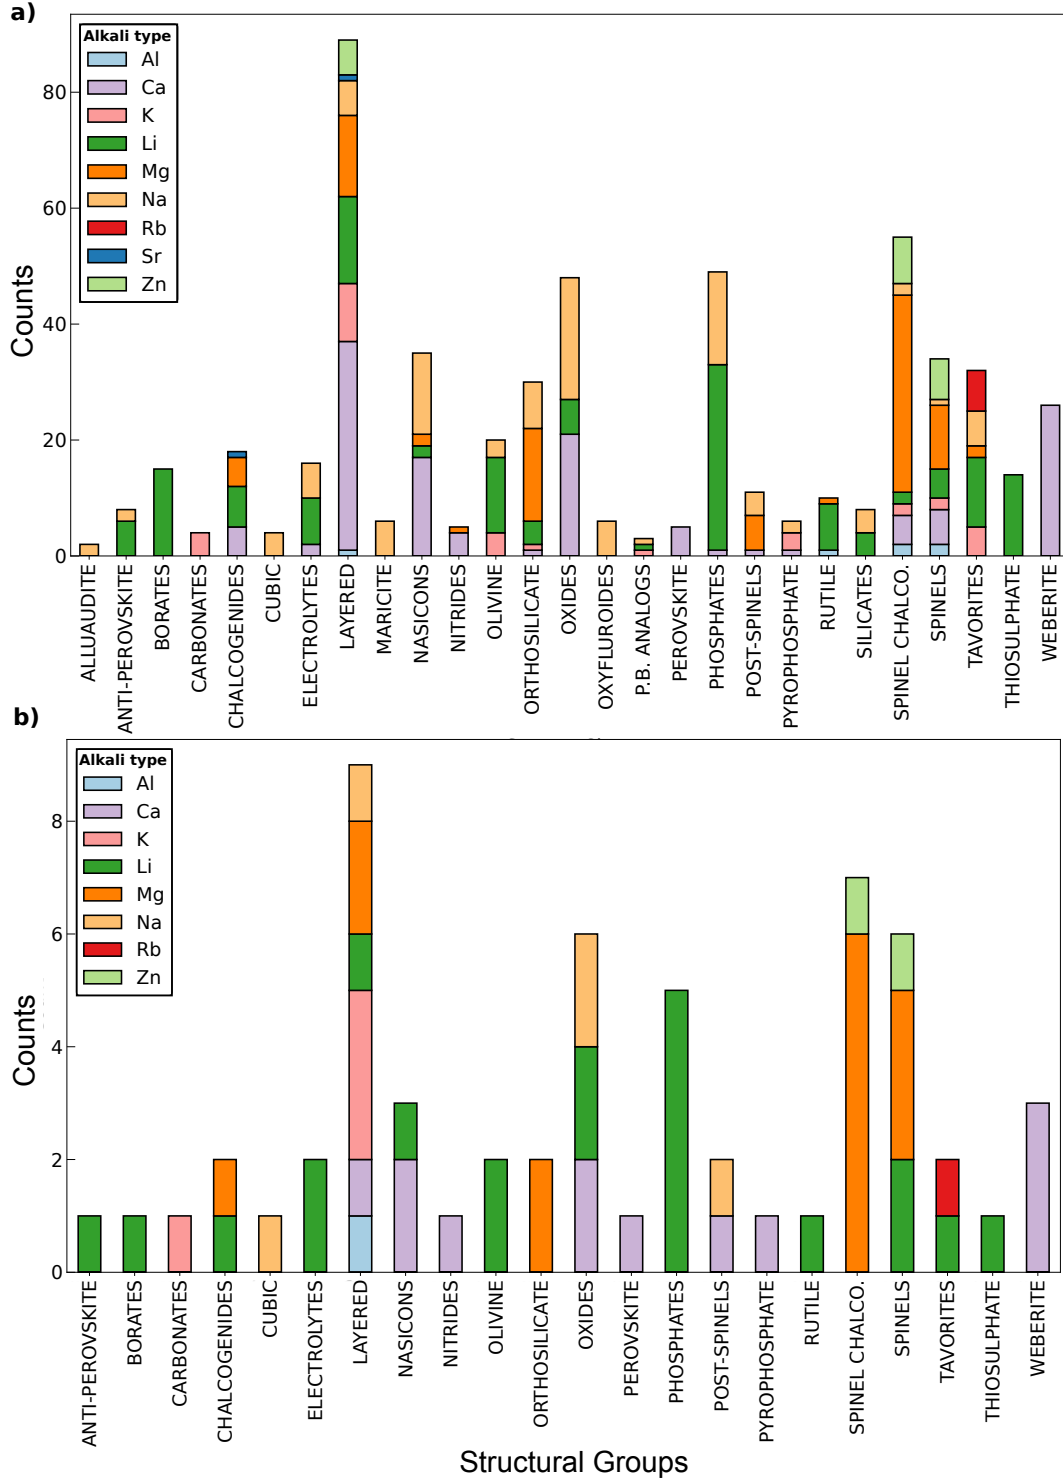


Figure 1: **Data distribution of training and test dataset** . Distribution of the data in the (a) train and (b) test datasets across different structural groups in the final dataset. The colored stacked bar heights within each bar corresponds to the contribution from different intercalant ions within that structural group.

Here, we use a curated dataset comprising 619 distinct migration pathways (see Figure 1), across various ionic compounds that have been studied as electrode or solid electrolyte materials for batteries, and the corresponding E_m derived from DFT-NEB calculations. The overall dataset is available at Ref. 53, as part of our additional work. The dataset encompasses both discharged (71.4%) and charged states (23.6%) of the electrodes, with intermediate compositions (5%) included in select instances. Note that we refer to electrode materials with high intercalant compositions (e.g., $x \sim 1$ in Li_xCoO_2) as the corresponding discharged states, while low intercalant compositions ($x \sim 0$ in Li_xCoO_2) constitute charged states.

The majority (88.12%) of the collected E_m values were calculated using the generalised gradient approximation (GGA) [56] as the XC functional, with other datapoints calculated with the Hubbard U [57] corrected version of GGA (or GGA+ U), the strongly constrained and appropriately normed [58] functional, and the localised density approximation. [59,60] E_m values were initially gathered from published literature, and the corresponding crystal structures were obtained from the MP or the inorganic crystal structure database. [61] In cases where structures were unavailable, ground state (GS) structures were generated from appropriate parent structures using reference lattice scaling [62] to modify the lattice parameters and/or by enumerating possible ordered configurations via the OrderDisorderedStructureTransformation class within the pymatgen package, [63] and subsequent relaxations with DFT. [53]

The dataset spans 58 distinct space groups, categorised into 27 structural groups, with migration barriers ranging from 0.03 to 8.77 eV. Prominent structural groups in our dataset include spinels, layered, olivines, tavorite, phosphates, weberites, and NaSICONs. As much as possible, we used structural groups that are quite common in the battery literature. Layered structures constitute the largest portion of the dataset, with 98 entries, followed by spinel chalcogenides, phosphates, and the general class of oxides. Other structural groups, such as alluaudites, Prussian blue analogs, and carbonates, are also represented, albeit with fewer data points. Lithium (Li)-based intercalants account for approximately 28.3% of the dataset, followed by calcium (Ca), sodium (Na), magnesium (Mg), potassium (K), zinc (Zn), strontium (Sr), aluminum (Al), and rubidium (Rb). Further details regarding the complete dataset generation, distribution of datapoints, and comprehensive descriptions of each datapoint can be found in Ref. 53. The split of the dataset into train and test subsets for model training and evaluation and the data distribution in each subset is described in the Methods section and visualized in Figure 1.

3 Results

3.1 Architectural modifications

Specific architectural modifications were necessary to adapt and FT our previously developed MPT model [52] for the prediction of E_m . A key objective of our final trained model is that it should be able to distinguish multiple migration pathways within the same crystal structure, since that is quite typical in ionic solids. A classic example of a structure with multiple migration pathways is the layered- Li_xCoO_2 , where the Li migration along Li layers is significantly faster compared to a Li migration across the Co layers. Thus, distinguishing multiple migration pathways requires that the model be provided an inductive bias on the direction of motion of the migrating ion. We provided the directional information by either considering both initial and final configurations along the migration pathway as inputs to the modified MPT model or in the form of a set of interpolated images (i.e., a band) between the initial and final images as an input. While including the initial and final configurations only accounts for the direction of motion, the band input also

includes partial information on the transition state geometry.

Additionally, we varied the number of convolutions performed during FT, and also added attention-based pooling mechanisms to refine the embedding of the local geometries around the migration path. These modifications led to four different FT model architectures, namely MODEL-1 (orange lines), MODEL-2 (green), MODEL-3 (blue), and MODEL-4 (magenta), as illustrated in Figure 2a. Each model uses either one or two copies of the MPT model and the solid (dashed) lines in Figure 2a indicate cases where four (one) convolutions are performed during FT. Briefly, MODEL-1 includes two MPT instances and takes the initial and final configurations as inputs and pools the output of both instances (via addition, subtraction or concatenation) before E_m predictions. MODEL-2 is similar to MODEL-1 but takes in a difference vector (“delta”) of embeddings between the initial and final configurations and concatenates the delta to the initial configuration embeddings. MODEL-3 is a single MPT instance that takes the interpolated band as the input. MODEL-4 builds upon MODEL-3 by adding attention blocks to two MPT instances, one that takes the full structure with the interpolated band and another that takes a sub-graph that focusses on the local environment of the band. Detailed descriptions of all FT model architectures, including scratch models, are provided in the Methods section.

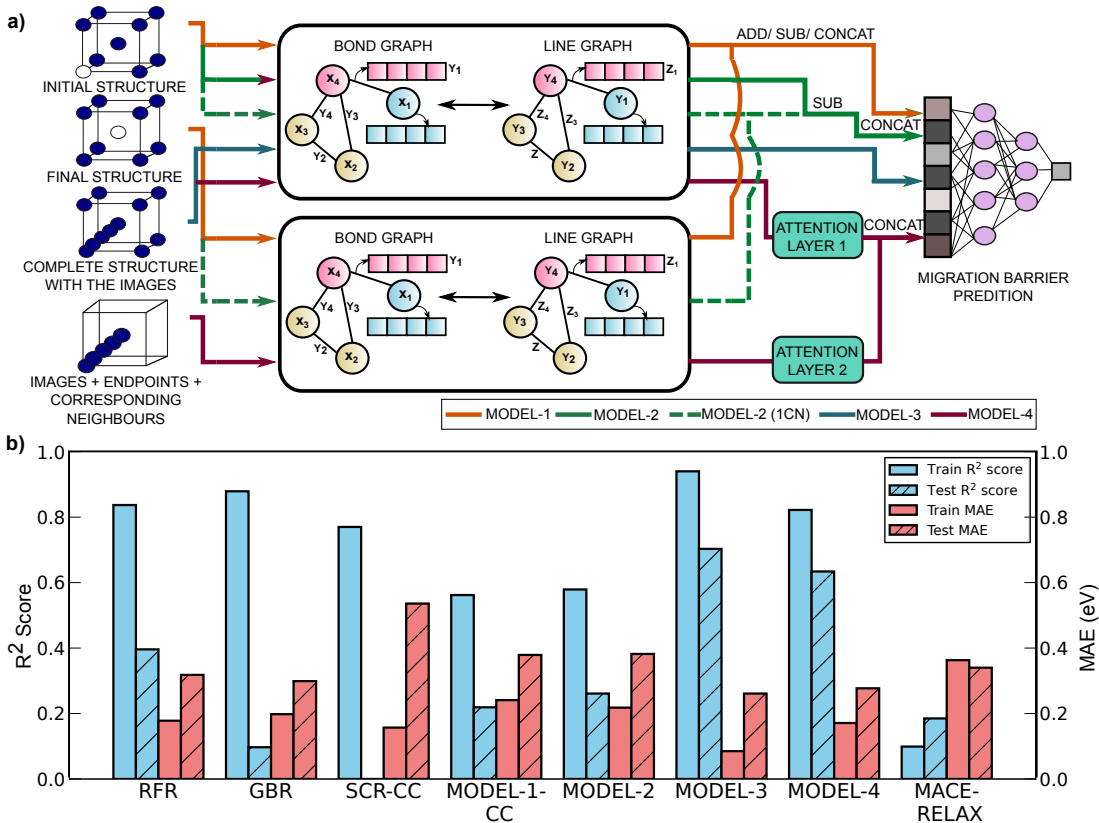


Figure 2: **Modified MPT architectures used for FT and train/test scores of different models.** (a) The four different modified MPT architectures explored in this work, namely MODEL-1 (orange lines), MODEL-2 (green), MODEL-3 (blue), and MODEL-4 (magenta). Solid (dashed) input/output lines correspond to four (one) convolutions performed on the MPT model. (b) R^2 scores and MAE for all models. The left (blue bars) and right (pink bars) y-axis values represent R^2 scores and MAEs (in eV). Solid and hashed bars denote the train and test scores, respectively.

3.2 Performance of classical and scratch models

Figure 2b illustrates the R^2 scores and MAEs for both training (solid bars) and test (hashed bars) datasets for different models, including classical ML models, scratch models (SCR), FT models, and DFT-NEB calculated E_m using a universal MLIP (denoted as MACE-RELAX). Blue (pink) bars and the left (right) y-axis values represent the R^2 scores (MAEs in eV). For models with multiple scenarios, the best-performing model scores are selected for the plot. For example, MODEL-1 has three different scenarios depending on whether the final set of embeddings from the two MPT instances are added, subtracted, or concatenated (CC) and Figure 2b displays the scores for the MODEL-1-CC, which exhibits the best performance. The magnitude of the scores for all the models are tabulated in Table S5 of the supporting information (SI). Note that large negative R^2 scores (such as -1.241 for SCR-CC) are denoted as zeros for illustrative purpose. A model’s performance is considered good if it achieves both a high R^2 score and a low MAE.

Among the classical ML approaches, namely random forest regression (RFR) and gradient boosted regression (GBR), we observe RFR to outperform GBR on the test data even though GBR has better training scores, indicating that the GBR model was likely overfit. Importantly, our scratch models (SCR-CC in Figure 2b) perform inferior in comparison to the classical models in terms of both training and test scores. Among the scratch models, the model where the embeddings of the initial and final configurations were subtracted from each other (SCRATCH-SUB) exhibited the worst performance with highly negative R^2 scores, which is mainly due to the components of the embedding vector tending to zero after subtraction, thus failing to capture the small differences between the initial and final configurations. On the other hand, adding or concatenating the embedding vectors in scratch models offered better performance than SCRATCH-SUB.

3.3 Performance of TL models

Comparing the SCR-CC model with the FT MODEL-1 architecture, we find that TL does help in improving the performance of the graph-based model compared to scratch, with MODEL-1-CC showing a 29.3% decrease in test MAE compared to SCR-CC. However, MODEL-1-CC’s performance is still poorer in comparison to classical ML models, with a 19.2% higher test MAE than RFR (Figure 2b). The likely reasons for the inferior performance of MODEL-1-CC is its poor training scores, which can be attributed to MODEL-1-CC’s failure to distinguish multiple pathways within the same structure and eventually predicting identical E_m for different paths. Specifically, MODEL-1-CC failed to distinguish the distinct migration pathways in $\sim 81.1\%$ of systems that had multiple pathways in our training dataset. Thus, MODEL-1-CC is unable to utilize the initial and final configuration inputs to infer differences in the direction of migration. To verify that the poor learning of multiple pathways is the main bottleneck in the performance of MODEL-1-CC, we trained a variant of the model, MODEL-1-CC-SINGLE-PATH, using only a single migration pathway per structure in our train/test datasets. As anticipated, removing multiple pathways resulted in significantly improved training scores and enhanced test performance (test R^2 : 0.603, test MAE: 0.249, see Table S5). Thus, further modifications to the graph network architecture, going beyond MODEL-1-CC, are needed if models are to distinguish multiple pathways within the same structure.

To better capture the distinctions among multiple migration pathways, we modified the MODEL-1 architecture to generate MODEL-2, which emphasized the differences between the initial and final configurations via the calculation of the delta vector. Indeed, the proportion of datasets with multiple migration pathways that are not classified as distinct reduced to 71.1% within the training dataset with MODEL-2 compared

to MODEL-1 (81.1%). However, MODEL-2 exhibited only an improvement of 3.02% and 19.18% in terms of training and test R^2 scores, with a corresponding increase in test MAE of 0.8%, compared to MODEL-1. Importantly, MODEL-2’s performance remains poorer than classical ML models, suggesting that even better modifications to the graph network are necessary.

To improve the ability of the graph network to identify different migration directions, we generated MODEL-3, which is a standard MPT model architecture but with the input structures augmented with positional data from three interpolated images alongside the initial and final sites. Including the interpolated images creates a band representation, or a guess of the pathway along which the ion is likely to migrate, with some information of the transition state. Including the band representation significantly improved the performance of the MPT model after FT, with MODEL-3 posting a 77.52% increase in test R^2 score (0.703) and a 17.92% decrease in test MAE (0.261 eV) compared to the RFR model (Figure 2b). Thus, incorporating information on the band provides a clear intuitive bias to the graph model on the direction of motion, and the model is able to distinguish different pathways within the same structure, resulting in a clear performance improvement on the test set. Notably, only 27.2% of the training datapoints corresponding to multiple migration pathways had their absolute errors greater than 0.1 eV with MODEL-3.

In an effort to enhance the emphasis on interpolated images, we integrated attention layers, a fundamental component of transformer architectures widely utilised in large language models [64,65] and created MODEL-4. Attention blocks facilitate the creation of context-aware embeddings, significantly improving tasks such as text generation and translation in language models. We adapted the attention architecture by employing atom embeddings as inputs to generate query, key, and value vectors, thereby enabling an understanding of atomic interactions or the “attention” between atoms within the structure. In principle, including attention should heighten the model’s sensitivity to critical features that influence E_m predictions, since MODEL-4 leverages embeddings obtained directly from the attention layers. Indeed, MODEL-4 achieves superior test R^2 scores and MAEs compared to RFR (Figure 2b) and is able to distinguish multiple migration pathways within the same structure, similar to MODEL-3. However, MODEL-4’s test R^2 scores are $\sim 9.82\%$ lower and its train MAEs are $\sim 101.18\%$ higher than those of MODEL-3. The test MAE values for MODEL-3 and MODEL-4 are quite similar (6.13% deviation). Thus, we find that adding attention layers to MODEL-3 is not necessarily a helpful addition to improve performance, with MODEL-3 being the best FT model we have so far.

Given that our dataset is new, we benchmark our models against a universal MLIP (MACE-MP-0 [54,55]), which was used as the energy and force evaluator in NEB calculations (Figure 2b). Since the initial and final configurations in our dataset were predominantly unrelaxed structures (with DFT), we considered NEB calculations with MACE, both including initial/final configuration relaxation (MACE-RELAX in Figure 2b) and excluding any relaxation. Unsurprisingly, the MACE-NEB calculations with initial/final configuration relaxation significantly outperformed the calculations without any relaxations, with R^2 scores and MAEs of 0.185 and 0.340 eV on the test dataset, respectively. Despite a test MAE that is only 30% higher than MODEL-3, MACE-RELAX had a notably lower R^2 score, indicating its inability to capture qualitative trends in E_m effectively. Additionally, while MACE-RELAX is able to distinguish different pathways in a structure, the absolute errors of MACE-RELAX predictions in such cases are significantly higher than MODEL-3. For example, in Na-orthosilicates ($\text{Na}_2\text{FeSiO}_4$) and Ca-weberites ($\text{Ca}_{1.5}\text{Ni}_2\text{F}_7$), the absolute errors in identifying multiple pathways varied between 1-2.5 eV with MACE-RELAX compared to 0.003-0.17 eV with MODEL-3. Thus, we find our FT MODEL-3 to be better at both quantitative and qualitative predictions of E_m compared to MACE-RELAX. This analysis also underscores the importance of using both

R^2 and MAE metrics to comprehensively assess a model’s performance.

3.4 Predictions vs. target

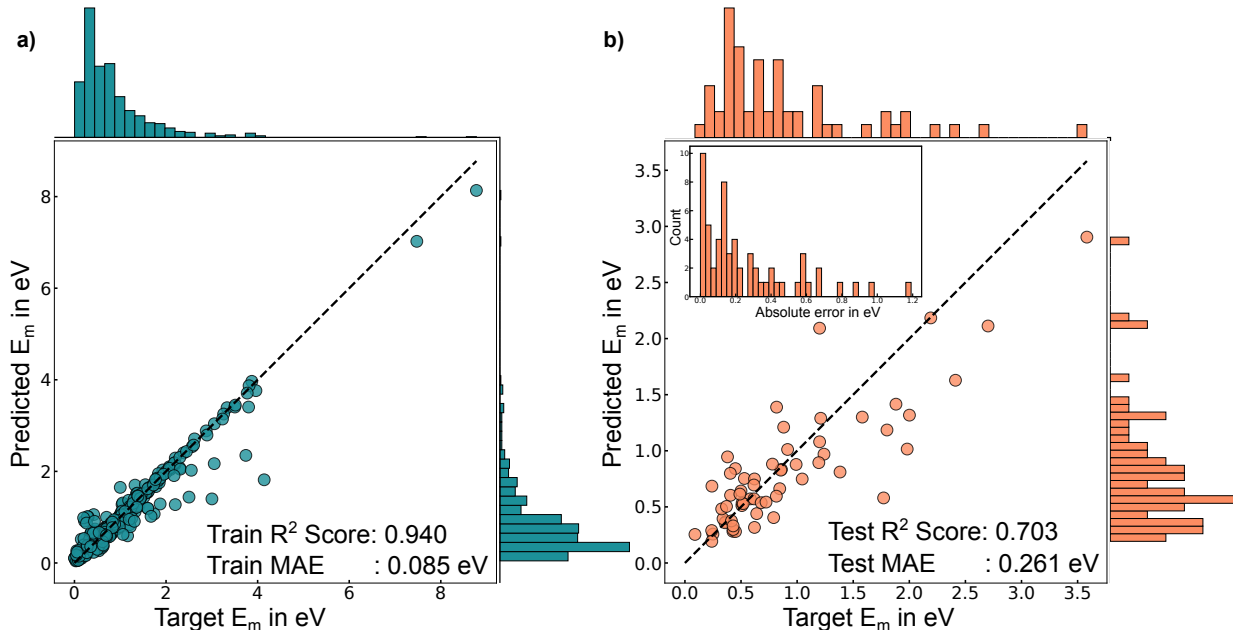


Figure 3: **Prediction vs. target E_m .** Parity plots for a) training and b) test datasets, respectively. The inset histogram in panel b shows the frequency distribution of the absolute error range in eV. The histograms on the right and top margins illustrate the frequency distribution in the prediction and target E_m in both datasets.

Panels a and b of Figure 3 depict the comparison between the predicted and the target E_m values for the training and test datasets, respectively, for our best-performing model, MODEL-3. The prediction versus target parity plots for other models are compiled in Figures S2 and S3 of the SI. The accompanying histograms along the x- and y-axis in Figure 3 margins show the distributions of target and predicted E_m values. Both training and test R^2 scores and MAEs are indicated within the panels. Although the frequency of under- and over-predictions with MODEL-3 in the training set is similar, under-predictions tend to have larger absolute errors compared to over-predictions. Specifically, 12 out of 19 datapoints with absolute errors greater than 0.5 eV are under-predicted by MODEL-3, averaging an error of approximately 0.99 eV. The highest under-prediction error occurs in oxide- CaCu_2O_3 , with a predicted E_m of 1.82 eV against a target of 4.14 eV. Notably, 11 of these 12 under-predicted datapoints have target E_m exceeding 1.5 eV, except for LiFeBO_3 (space group: P21/c, path: 4) with a target E_m of 1.16 eV. Among the 12 under-predictions, five cases involve oxides and borates.

The inset histogram in Figure 3b illustrates the frequency distribution of absolute errors in the test dataset by MODEL-3. Importantly, $\sim 32\%$ of the test datapoints predicted by MODEL-3 have an absolute error below 0.1 eV, representing high accuracy in the predictions of MODEL-3. Additionally, 38% fall within a moderate accuracy range (0.1 to 0.3 eV absolute error), while 30% exceed an absolute error of 0.3 eV, indicating low accuracy. The lowest absolute error (< 0.1 eV) in the test dataset is observed in the case of spinels and spinel chalcogenides, which contribute about 16% of the training dataset and contain fairly

typical tetrahedral-octahedral-tetrahedral migration pathways. [66] Of the 18 test datapoints with absolute errors greater than 0.3 eV, the average MAE across the 18 datapoints is ~ 0.60 eV with 11 E_m values being under-estimated by more than 0.5 eV by MODEL-3. The highest absolute error in this group is observed for KNiF_3 , with a target E_m of 1.77 eV and an under-prediction error of 1.19 eV, which may be due to the high levels of distortions that the perovskite NiF_3 is subjected to as K^+ moves across the structure and not captured in our model.

The frequency of under- and over-predictions of E_m across the four FT models is similar (Figure S2), except MODEL-2 that exhibits about 20% more instances of over-prediction on average during training. Approximately 57% and 54.7% of training samples from MODEL-1 and MODEL-2, respectively, achieve an absolute error below 0.1 eV. In comparison, MODEL-3 and MODEL-4 achieve significantly higher accuracy, with 81.6% and 58.3% of their training samples that have an absolute error below 0.1 eV. Additionally, samples with absolute errors equal to or exceeding 0.5 eV constitute around 12% for MODEL-1 and 10% for MODEL-2, 3% for MODEL-3, and 6% for MODEL-4, which explains the superior training MAE observed in MODEL-3 (Figure 3a). While these training statistics may suggest that MODEL-3 and MODEL-4 are overfitting to the training dataset, the fact that both models exhibit superior performance on the test set (Figure 3b and Figure S2f) compared to MODEL-1 and MODEL-2 indicate that models with band inputs do generalize better to predict E_m compared to models that take only the initial and final configurations as input.

3.5 Distinguishing migration pathways

The ability of different models to distinguish multiple migration pathways within the same structure is illustrated using race-track plots in Figure 4a, which displays predictions made among training datapoints. We selected representative systems (Li_3OCl , $\text{Ca}_2\text{Mn}_2\text{O}_5$, MgMnSiO_4 , and VOPO_4 , top x-axis of Figure 4a) featuring two or three distinct migration pathways (bottom x-axis) and involving four different intercalants (Li, Ca, Mg, and Na) that are major contributions to the dataset for this analysis. The y-axis in Figure 4a represents the E_m values in eV, with target values highlighted by horizontal black dashed lines within each track. Note that the VOPO_4 structure considered for this analysis is its charged state with Na as the intercalant - hence the notation ' $\text{VOPO}_4\text{-Na}$ '. The tracks are color-coded to differentiate among the intercalants, with the FT models indicated by different colored symbols.

Data from Figure 4a indicate that MODEL-1 (pink diamonds) consistently predicts identical E_m across different pathways within the same structure, for all systems, indicating MODEL-1's inability to distinguish different paths. In contrast, MODEL-2 (blue triangles) shows variations in predicted E_m across different pathways, albeit with substantial errors in its predicted E_m versus the target. Thus, the inductive bias introduced in MODEL-2 is able to distinguish pathways compared to MODEL-1 for the systems in Figure 4a. Similarly, MODEL-3 (green circles in Figure 4a) and MODEL-4 (orange squares) are able to distinguish different pathways as well, indicating that band inputs are useful as tools to add inductive bias with respect to the direction of migration. While MODEL-3 and MODEL-4 exhibit predicted E_m values that are closer to the target values, the data points in Figure 4a are within the training set and hence not a direct reflection of the generalizability of these models.

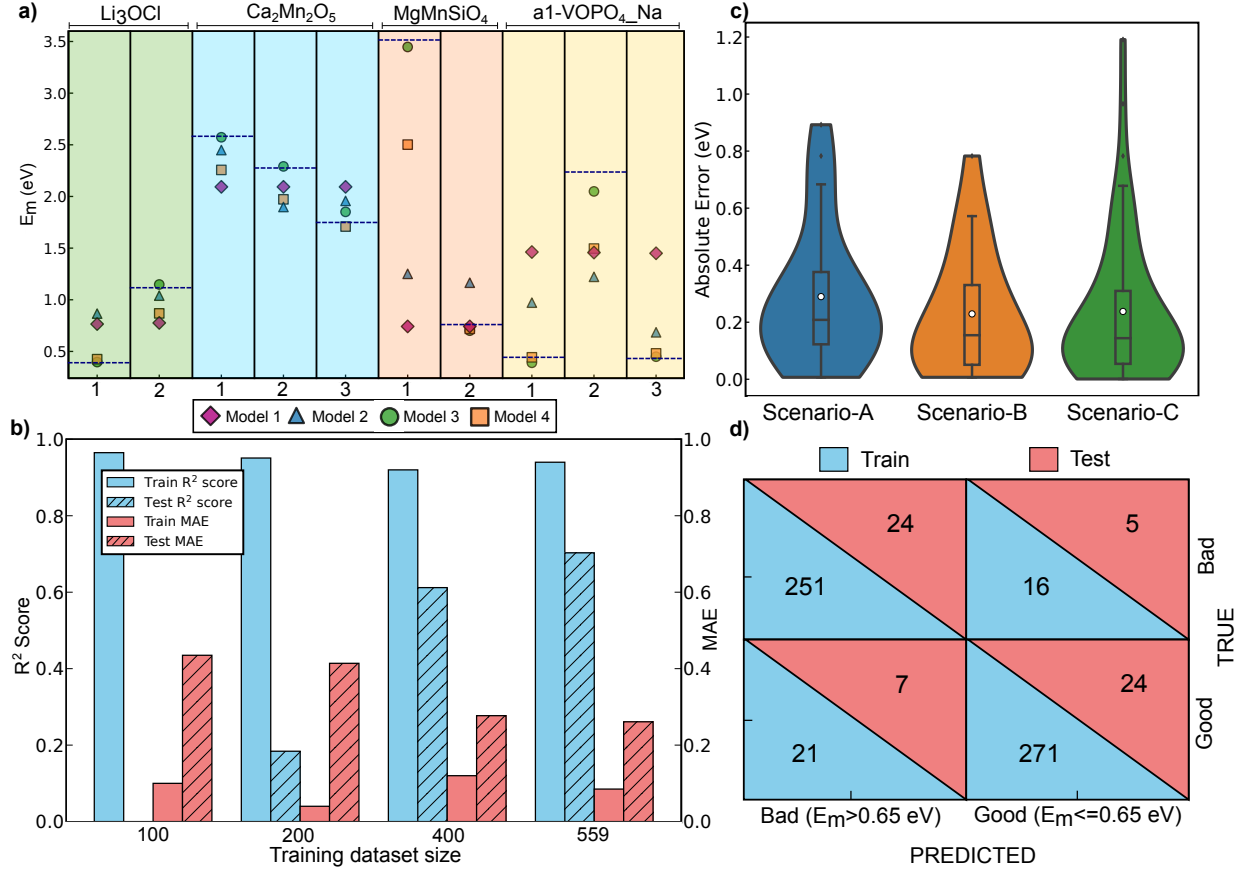


Figure 4: **Analysis of model performance.** a) Race-track plot illustrating the predictions made by the four different FT models (represented by distinct colored symbols) for different pathways in a given structure. ‘a1’ refers to a specific VOPO_4 polymorph of space group $P4/n$. Horizontal lines are the target E_m values for each path. b) Bar chart showing the train and test scores of MODEL-3 with different FT train dataset sizes. c) Violin plot signifying the distribution of absolute errors among the test datapoints under scenarios A (blue), B (orange), and C (green). d) Confusion matrix quantifying the classification performance of MODEL-3 in the train (upper blue triangles) and test (lower pink) datasets.

3.6 Influence of dataset size

To quantify the influence of dataset size during FT on the prediction accuracies for the best-performing MODEL-3, we plot the train and test R^2 scores and MAEs for three lower FT dataset sizes, namely 100, 200, and 400 in Figure 4b. Note that 559 is the maximum training set size of our E_m dataset, while the test dataset remained the same for all training dataset sizes. The notations used in the figure are identical to Figure 2b. As expected, we observe significant improvement in the test scores (both R^2 and MAE) as the training dataset size increases. Also, the model that uses 559 training datapoints offers the best train as well as test scores. The significant disparity in the train and test scores for models trained with lower dataset sizes (especially at 100 and 200 datapoints in Figure 4b) indicates the tendency of the model architecture to overfit at very small train dataset sizes.

3.7 Generalization across pathway, composition, and chemistry

To better understand the generalization abilities of MODEL-3 and its possible use as a screening tool for battery applications and beyond, we analyze its performance over three different scenarios that are encountered in the train/test datasets (see Figure 4c). Scenario A involves structures where one migration pathway is in the test set, while the remaining pathway(s) are in the train set, quantifying the model’s ability to generalize across different migration pathways. Scenario B consists of systems where the charged (or discharged) composition appears in the train set, while the corresponding discharged (charged) state appears in the test set, signifying the model’s ability to generalize across compositions of an intercalant within a host framework. Scenario C determines the model’s generalizability across different chemistries since it encompasses instances where either the intercalating ion or the host structure’s anion/cation in the test set differs from what the model has seen in the train set.

Figure 4c plots the absolute error (in eV) in the E_m predictions on the test set for the three scenarios as violins. The lower and top edges of the violins correspond to the range of the absolute error for each scenario. The empty circle is the mean, and the solid black line is the median of the distribution. Scenarios B and C have similar mean (~ 0.23 eV) and median (~ 0.14 eV) absolute errors that are lower than Scenario A (~ 0.29 and 0.20 eV), and have a larger number of data points with low absolute errors (< 0.1 eV). This indicates that MODEL-3 generalizes better across intercalant composition and chemistry compared to migration pathways. Additionally, prediction confidence is highest for scenario C (followed by scenarios B and A), as 68% of systems in scenario C have a test MAE of 0.11 eV (i.e., in the high/moderate accuracy range). Thus, our analysis suggests that MODEL-3 can offer robust predictions for a given system when it has seen structurally (not necessarily compositionally or chemically) similar systems during training, which can be quite useful when used as a screening tool. Importantly, our analysis indicates that distinguishing directionality of migration within the same structure is perhaps the hardest task for the graph network architectures considered in this work, highlighting the role of difficult-to-describe local coordination environments in differentiating E_m .

3.8 Classification metrics

To examine if MODEL-3 can be used as a screening tool to classify structures as good ($E_m \leq 0.65$ eV) or bad ($E_m > 0.65$ eV) ionic conductors, instead of being used as a ‘regression’ tool to predict absolute E_m , we segregated the datapoints that fall into the above two categories in both the train and test sets. Figure 4d illustrates the confusion matrix, which tabulates MODEL-3’s performance in identifying a good or a bad conductor in the train (lower blue triangles) and the test (upper pink) sets, respectively. The overall accuracy of the test (train) predictions is 80.0% (93.4%), which represents the number of correct predictions in the overall test (train) samples, highlighting the potential use of MODEL-3 as a classifier of structures as good/bad conductors. The sensitivity (recall) or the ability of the model to classify actual good and bad conductors in the test set is 77.4% and 82.8%, respectively. Notably, the precision in classifying good conductors is higher (82.8%) than that of bad conductors (77.4%), implying that statistically MODEL-3 is marginally less likely to falsely classify a structure to be a good conductor than a bad conductor. Note that the threshold criterion in identifying good and bad conductors in this analysis ($E_m = 0.65$ eV) is arbitrary, and using a different threshold will modify the confusion matrix.

4 Discussion

For the accurate estimation of E_m in ionic solids, we present a MPT model that has been modified and FT specifically for precise E_m predictions over a wide range of crystal structures and migration pathways. Via modifications to the pre-trained MPT model to introduce inductive bias on the directionality of a migration path, we FT four different MPT model architectures on a curated dataset of 619 DFT-NEB-calculated E_m values obtained from literature. Importantly, we find our MODEL-3 architecture, that takes a band input, to be the best performing, with test R^2 and MAE of 0.703 and 0.261 eV, respectively. We observe MODEL-3 to not only distinguish multiple pathways in a given structure, but also generalize well across intercalant chemistries and compositions. Furthermore, we find that MODEL-3 can be used as a classification tool, with an accuracy rate of 80% on classifying a structure as a good ($E_m \leq 0.65$ eV) or a bad ($E_m > 0.65$ eV) conductor. Thus, our best-performing model should be a useful tool in the screening of materials with high μ for battery applications and beyond.

The performance of FT models can be further improved by including a larger number of data points in our dataset, which will require more systematic DFT-NEB calculations. Note that we expect our FT models to outperform scratch models with additional data, given that the FT models that are trained with fewer data points (~ 200 , Figure 4b) exhibit similar performance to scratch models trained on the full dataset (Figure 2b), identical to our observations in our previous work. [52] In addition to presenting MODEL-3 for efficient E_m predictions, our study highlights possible strategies to modify the MPT model for targeted FT on specific datasets. Our proposed modifications (in Figure 2a) allow (partially) capturing global and local structural details that correlate directly with our target property (E_m). Thus, similar modifications of our MPT model, with careful hyperparameter optimization, can be used for FT on different target properties (such as adsorption energies on surfaces, point defect formation energies, etc. [67]) that are difficult to calculate/measure.

The predictive accuracy of our best-performing MODEL-3 still remains considerably lower than the R^2 scores and MAEs reported in our previous work [52] for ‘simpler’ property predictions, such as formation energy (R^2 and MAE of 0.774 and 0.089 eV). We attribute this lower accuracy to three factors. First, the model may have inadequate level of inductive bias resulting in insufficient learning of both local and global structural features that determine E_m . Second, the dataset may contain intrinsic noise, since all E_m have not been calculated at the same level of theory and ensuring all E_m are at the same level of theory is beyond the scope of this work. Third, ALIGNN only considers bond and angle embeddings and using more advanced GNN architectures that consider many-body interactions may improve prediction accuracy.

We observe that MODEL-3 seems to generalize more efficiently across intercalant compositions and chemistries than it does across different migration pathways within a specific structure (Figure 4c), which can be attributed to the following factors. First, the underlying migration pathway can be identical (or similar) across different material compositions and chemistries. For instance, spinel structures exhibit a consistent tetrahedral-octahedral-tetrahedral migration path regardless of whether the composition is charged or discharged. Also, the migration path in spinels remains the same irrespective of variations in the migrating ion, transition metal cation, or the anion. Thus, if a model learns the key factors contributing to the E_m in one spinel structure, it may be able to generalize well on other spinels. Indeed, we find MODEL-3’s prediction accuracy to be high for spinels (absolute errors in $E_m < 0.1$ eV). Second, the magnitude of E_m can be determined by local structural ‘motifs’ that define the migration pathway. While global structural features like lattice parameters, composition, and transition metal/anion identity determine the overall potential energy landscape, local structural features (such as coordination number changes, bond distances,

rotation or distortion of polyhedral units) dictate the 'local' energetics near a saddle point. Thus, limitations in the model's ability to capture the importance of such local features may affect its generalization ability.

Surprisingly, the addition of attention blocks into MODEL-3 (resulting in MODEL-4, Figure 2a) did not yield a significant enhancement in the predictive accuracy (Figure 2b). Our rationale for the inclusion of attention blocks was to provide the model with a better understanding of the "context" or importance of an atom or a local structural motif along the migration pathway. This is why we employed the dual-input approach, where we used the overall band and the sub-graph of the band's local coordination environment. One possible reason for the ineffectiveness of attention blocks is the limited size of our dataset. Indeed, attention layers have been demonstrated to be highly effective in large language models trained on billions of tokens, [68] while we only have a total of 619 data points. Nevertheless, as the scientific community contributes and makes the E_m dataset more general, it will be worthwhile to revisit the utility of attention blocks in extracting atom-level importance in material property predictions.

MACE-NEB-RELAX exhibited convergence difficulties in 68 systems, which may be potentially resolved by adjusting BFGS steps, interpolation methods, or other hyperparameters. In certain cases, convergence issues observed in MACE-NEB-NO-RELAX were resolved upon relaxing the initial and final images. Across the complete dataset, MACE-NEB-RELAX achieved an overall R^2 score of 0.10 and an MAE of 0.36 eV, emphasizing MODEL-3's superior accuracy. Despite its low R^2 score, MACE-NEB-RELAX provided accurate E_m estimations and reasonable geometries for intermediate images upon a NEB calculation, particularly for 'simple' systems containing single anions such as spinel oxides, spinel chalcogenides, post-spinels, and layered structures. If convergence challenges can be mitigated, output geometries from MACE-NEB-RELAX can serve as initial guesses for DFT-NEB calculations, which may reduce computational costs.

5 Conclusion

In conclusion, precise E_m estimation is paramount for quantifying ionic conductivity, a material property that is crucial in selecting materials for batteries and other applications. Building upon our previous work involving simultaneous PT of a graph-based neural network on seven bulk material properties, we introduced four modifications into a MPT model to build inductive bias on distinct migration pathways within a structure. Subsequently, we FT each model using a curated dataset of 619 DFT-NEB-calculated E_m values sourced from literature for precise E_m predictions across various migration pathways, structural frameworks, and intercalant chemistries. MODEL-3, which involved a single MPT model instance that took a band configuration as input, demonstrated the best performance, achieving a R^2 score of 0.703 and a MAE of 0.261 eV on the test set and successfully identified multiple migration pathways within a structure. Additionally, MODEL-3 showed an ability to generalize well across intercalant compositions and chemistries. Furthermore, MODEL-3 effectively classified good ($E_m < 0.65$ eV) and bad ($E_m > 0.65$ eV) ionic conductors, achieving 82.8% precision and 77.4% sensitivity for identifying good conductors, highlighting its possible use in high-throughput screening approaches to identify novel materials. Beyond improved E_m predictions, our work demonstrates effective strategies for adapting and modifying PT graph architectures to FT on material properties that are scarcely available, thereby addressing a critical challenge of data insufficiency for ML in materials science.

6 Methods

6.1 Data processing

The dataset generated from Ref. 53 was split into the training and test set in the ratio, 90:10. Our final test set consists of 60 datapoints across 21 distinct structural groups, with the training set consisting of 559 datapoints across 27 groups. As established in our previous work, [52] it is important to standardise and normalise the target metric when we PT/FT on different properties of varying scales and units. Thus, we standardized and normalized the training and the test datasets using the training data statistics, namely, the minimum, the maximum, the mean, and the standard deviation.

Panels a and b of Figure 1 show the stacked bar charts illustrating the data distribution across the structural groups in the training and the test datasets, respectively. The length of each color-coded stacked bar in each panel of Figure 1 represents a unique intercalant and is equal to the number of datapoints with the corresponding intercalant in that structural group. Our goal in splitting the train and test subsets was to generate a structurally diverse test set with a focus on the most prevalent structural groups in the training data, which ensures that model performance is mainly assessed on groups with sufficient training data while also including structural diversity. We carefully constructed the test dataset by using the following strategies:

1. Quasi-weighted distribution: The data distribution in the test set is similar to the distribution of structural groups found in the training set, ensuring a balanced evaluation.
2. Structural groups constituting between 1-2% of the complete (train+test) dataset were represented by a single datapoint in the test set. This prevents the model from being unfairly penalized due to limited exposure to these groups during training. Examples of structural groups identified in this step include rutile, pyrophosphate, perovskite, nitride, anti-perovskite, borates, and carbonates.
3. The test set excluded structural groups with limited representation in the overall dataset (i.e., <1%). We also excluded structural groups from the test set with similar chemical compositions to those already present in the test set but with different space groups, even if their contribution to the overall dataset is slightly >1%. For example, we excluded silicates that comprise $\sim 1.2\%$ of the overall dataset from the test set, because we already included orthosilicates with similar composition but different space groups in the test set. This strategy prioritizes more abundant and structurally distinct groups in the test dataset, thus providing a robust evaluation of our models.
4. Random sampling within groups: Once the desired percentage contribution for each structural group was determined, datapoints were randomly selected from the pool of available data to represent that group in the test set.

6.2 Graph network model and pre-training

GNNs are well-suited for capturing the inherent atomic connectivity within crystal structures, leading to improved property predictions. We employed the ALIGNN architecture, a GNN variant, due to its demonstrated ability to enhance accuracy of material property predictions and to generalize on out-of-distribution tasks. [52,69] The ALIGNN architecture, typically comprising seven layers, processes atom (X), bond (Y), and bond-angle embeddings (Z) in layers 1, 2, and 3, respectively. The X, Y, and Z embeddings serve as input to layers 4 and 5, which perform edge-gated graph convolutions (E-GGC) multiple times. [70]

The outputs from layers 4 and 5 (typically referred to as the ALIGNN layers) are pooled and subsequently passed through a multi-layer perceptron (MLP) to generate a property prediction. Further details regarding the construction of GNNs and the ALIGNN architecture are available in the literature. [51, 71, 72] The default ALIGNN architecture that we employed and the associated hyperparameters are compiled in Section S1 and Table S1 of the SI.

The generalised MPT model, as developed in our previous work, [52] was trained on a comprehensive multi-property dataset. Specifically, the MPT model was constructed by modifying the final MLP layer of the ALIGNN architecture to include seven prediction heads, each corresponding to one of the seven material properties, as illustrated in Figure S1 of the SI. Each data point (structure) is mapped to a one-hot encoded vector and a property vector of dimension 7, where the former indicates the availability of a specific property for the structure and the latter contains the corresponding property values. We modified the loss function, as in Equation 2, where y_p and y_t represent the predicted and target values, i is the property index, N is the number of properties, and δ^i is the entry of the one-hot encoded vector for property i . This MPT model, which was trained simultaneously on all seven properties, [52] was utilised as a PT model for FT on the target property (E_m) in our work.

$$\mathcal{L} = \frac{1}{N} \sum_{i=1}^N |y_p^i - y_t^i| \delta^i \quad (2)$$

6.3 Fine-tuning model architectures

Figure 2a illustrates the four model architectures explored in this work, which are explained in detail below. We designed a model architecture incorporating either one or two copies of the pre-trained MPT model, since a given MPT (or ALIGNN) model can take only one structure as an input. Each copy received either the initial or final or an interpolated band configuration of the migration pathway as input. During FT, the model was allowed to re-train fully on the E_m dataset (i.e., all weights and biases were allowed to be changed), with model parameter initializations coming from the MPT model, based on our observations of optimal FT strategies in our previous work. [52] The outputs from the (average) pooling or the attention layers of the MPT model(s) corresponding to the initial/final/band configurations were combined using various strategies (as explained below) before being passed to an MLP for the final property (E_m) prediction. Thus, we constructed four distinct model configurations for learning E_m , and the associated hyperparameters for each configuration is provided in Section S1 and Table S1 of the SI.

6.3.1 MODEL-1: Pooled Embedding Combination

In this model architecture (follow orange lines in Figure 2a), we initialized two instances of the MPT model, with one instance receiving the initial configuration of the migration pathway as its input and another receiving the final configuration. Following four E-GGC operations in the ALIGNN layers and subsequent pooling, the resulting embeddings from the two MPT model instances were either concatenated (CONCAT or CC), added (ADD), or subtracted (SUB) from each other before passing to a fully connected MLP with two hidden layers for E_m prediction. For illustrative purposes, empty circles within the cubic structures represent vacant sites in Figure 2a.

6.3.2 MODEL-2: Delta Vector Concatenation

Similar to MODEL-1, this model also uses two instances of the MPT model and is represented by the green lines in Figure 2a. The first embedding vector in this model was the pooled output following four E-GGC operations in the MPT instance that received the initial configuration as input. The second embedding vector, which we term the difference vector or delta, was calculated by subtracting the pooled vectors from two MPT models, with one instance receiving the initial configuration and the other instance the final configuration. Note that for calculating delta, the pooled vectors were obtained after one E-GGC operation instead of the standard four (as highlighted by dashed green lines instead of solid green lines in Figure 2a). Subsequently, the delta vector was concatenated with the first embedding vector and the resultant vector passed to the final MLP for E_m prediction.

6.3.3 MODEL-3: Interpolated Images

MODEL-3 is perhaps our simplest model that uses only one instance of the pre-trained MPT model and is indicated by blue lines in Figure 2a. The input to the MPT model in this architecture is the migration pathway, which we generate by a linear interpolation of three images between the initial and final atomic configurations. Note that linear interpolation is the typical technique utilized to initialize the MEP in DFT-based NEB calculations. Thus, the input to the MPT model is a single structure with initial, final, and three interpolated image sites being occupied by the migrating ion, with the resultant pooled vector (after four E-GGC operations) passed to the MLP for E_m prediction.

6.3.4 MODEL-4: Interpolated Images with Attention

MODEL-4 builds upon MODEL-3 by incorporating attention blocks to generate a refined pooled representation of the ALIGNN outputs, as represented by the magenta lines in Figure 2a. The objective of the attention-based pooling is to identify and prioritize the most influential nodes (atoms) of the structure for the target variable (E_m). To calculate the attention scores (A), we learn projection matrices that map the graph’s atom embedding vectors (X) to its corresponding query (Q), key (K), and value (V) representations, via learnable weights (W). ReLU stands for the rectified linear unit activation function.

$$Q, K, V = \text{ReLU}(XW_{Q,K,V})$$

Q and K are subject to batch matrix multiplication followed by processing through hyperbolic tangent and SoftMax functions to generate A . Subsequently, A is multiplied with V to produce an aggregated value tensor (X').

$$A = \text{SoftMax}(\tanh(QK^T))$$

$$X' = AV$$

The final output vector is the sum of the average-pooled X and the X' calculated within the attention block.

$$X'' = \text{mean}(X) + X'$$

In MODEL-4, we employed two different attention blocks, represented as ‘ATTENTION LAYER 1’ and ‘ATTENTION LAYER 2’. The former is applied on the embedding from the MPT model that takes the

complete structure with the interpolated images (or the main-graph) as the input. The latter takes only a sub-structure corresponding to the initial, final, interpolated images, and their corresponding neighbors (or a sub-graph) as the input. For generating the sub-graph, we considered neighboring atoms of each image that were within a cut-off distance of 3 Å from the corresponding image.

6.4 Model performance benchmarking

6.4.1 Scratch Models

We refer to scratch models as those modified ALIGNN architectures which were not pre-trained on any bulk property prior to being trained for E_m predictions. Thus, our scratch models provide a baseline for performance comparisons with our TL models. Specifically, we used two instances of the ALIGNN architecture to process two structures as input (i.e., the initial and final configurations, similar to MODEL-1), without any pre-training. The resultant embeddings from both instances were combined through addition (SCRATCH-ADD), subtraction (SCRATCH-SUB), or concatenation (SCRATCH-CC). We used this two-input-structure approach for training scratch models since the standard ALIGNN architecture is capable of taking only one input structure and any scratch resultant model will be incapable of identifying multiple migration pathways within the same structure.

6.4.2 Classical ML models

To establish a performance benchmark in addition to scratch models, we compared our MPT model against classical ML models, namely a RFR and a GBR. Both classical models were constructed using a comprehensive feature set that originated from two sources: the `matminer.featurizers` package within the `matminer` library, [73] and nine manually engineered features tailored to capture cation migration pathways. Matminer provided elemental, stoichiometric, electronic, environmental, structural, and interaction-based descriptors. Since RFR and GBR models cannot take two structures as input configurations simultaneously, we engineered the manual features to capture the characteristics of the migration pathway. The manual features included cation bond lengths, path distance, coordination number, and Voronoi polyhedra-derived attributes. The input structure to derive the features was the initial configuration of the migrating ion. From an initial set of 277 features, Pearson’s correlation coefficient [74] was used for feature selection. While we removed features that were highly correlated with each other, only features exhibiting some correlation (> 0.10) with the target variable (E_m) were retained, resulting in a final set of 75 features. The hyperparameters of both RFR and GBR were optimized using five-fold cross-validation scores. Details on the specific features used and the optimized hyperparameters are compiled in Section S2, Table S2, and Table S3 of the SI.

6.4.3 MACE-NEB E_m calculation

In addition to scratch and classical models, we compare the performance of our TL models with E_m predictions from NEB calculations, done with a universal MLIP, namely MACE-MP-0. [54, 55] For NEB calculations with MACE, we used the implementation available in the atomic simulation environment (ASE [75]). We performed the NEB calculations using two variations, one where we relaxed the endpoints using MACE-MP-0 before performing the NEB (we refer these predictions as MACE-NEB-RELAX or MACE-RELAX) and the other with no relaxation of the endpoints (MACE-NEB-NO-RELAX or MACE-NO-RELAX). Note that the MACE-NEB-NO-RELAX is the case that is similar to our TL model implementations, as we do

not relax the endpoints before training the model, except for the charged state structures that were relaxed with DFT to obtain the true GS. [53] Specifics on the NEB calculations performed using MACE and ASE are described in Section S3 and Table S4 of the SI.

7 Data availability

All computed data and constructed models associated with this work are available online freely to all via our GitHub repository.

8 Code availability

All codes related to this work are available online freely to all via our GitHub repository. The source code of ALIGNN is available at the GitHub repository maintained by the developers of ALIGNN.

9 Acknowledgements

G.S.G. and K.T.B. would like to acknowledge financial support from the Royal Society under grant number IES\R3\223036, and the United Kingdom Research and Innovation (UKRI) Engineering and Physical Sciences Research Council (EPSRC), under projects EP/Y000552/1 and EP/Y014405/1. G.S.G. acknowledges financial support from the Science and Engineering Research Board (SERB) of the Department of Science and Technology, Government of India, under sanction number IPA/2021/000007. R.D. thanks the Ministry of Human Resource Development, Government of India, for financial assistance. R.D. and G.S.G. acknowledge the computational resources provided by the Supercomputer Education and Research Centre, IISc, for enabling some of the calculations showcased in this work. We acknowledge National Supercomputing Mission (NSM) for providing computing resources of ‘Param Utkarsh’ at CDAC Knowledge Park, Bengaluru. PARAM Utkarsh is implemented by CDAC and supported by the Ministry of Electronics and Information Technology (MeitY) and Department of Science and Technology (DST), Government of India. Via our membership of the UK’s HEC Materials Chemistry Consortium, which is funded by EPSRC (EP/X035859/1), this work used the ARCHER2 UK National Supercomputing Service (<http://www.archer2.ac.uk>).

10 Author Contributions

G.S.G. and K.T.B. envisioned the project, supervised all aspects of the work, obtained funding and resources, and edited the manuscript. R.D. executed all aspects of the work, including data generation, data visualization, and writing the first draft of the manuscript.

11 Competing Interests

The Authors declare no competing financial or non-financial interests.

References

- [1] Patrice Simon, Yury Gogotsi, and Bruce Dunn. Where do batteries end and supercapacitors begin? *Science*, 343(6176):1210–1211, 2014.
- [2] John Christopher Bachman, Sokseiha Muy, Alexis Grimaud, Hao-Hsun Chang, Nir Pour, Simon F Lux, Odysseas Paschos, Filippo Maglia, Saskia Lupart, Peter Lamp, et al. Inorganic solid-state electrolytes for lithium batteries: mechanisms and properties governing ion conduction. *Chemical reviews*, 116(1):140–162, 2016.
- [3] Mohsen Sotoudeh, Sebastian Baumgart, Manuel Dillenz, Johannes Döhn, Katrin Forster-Tonigold, Katharina Helmbrecht, Daniel Stottmeister, and Axel Groß. Ion mobility in crystalline battery materials. *Advanced Energy Materials*, 14(4):2302550, 2024.
- [4] Sean D Griesemer, Yi Xia, and Chris Wolverton. Accelerating the prediction of stable materials with machine learning. *Nature Computational Science*, 3(11):934–945, 2023.
- [5] Phillip M Maffettone, Lars Banko, Peng Cui, Yury Lysogorskiy, Marc A Little, Daniel Olds, Alfred Ludwig, and Andrew I Cooper. Crystallography companion agent for high-throughput materials discovery. *Nature Computational Science*, 1(4):290–297, 2021.
- [6] Adolph Fick. V. on liquid diffusion. *The London, Edinburgh, and Dublin Philosophical Magazine and Journal of Science*, 10(63):30–39, 1855.
- [7] Ziqin Rong, Rahul Malik, Pieremanuele Canepa, Gopalakrishnan Sai Gautam, Miao Liu, Anubhav Jain, Kristin Persson, and Gerbrand Ceder. Materials design rules for multivalent ion mobility in intercalation structures. *Chemistry of Materials*, 27(17):6016–6021, 2015.
- [8] Yan Wang, William Davidson Richards, Shyue Ping Ong, Lincoln J Miara, Jae Chul Kim, Yifei Mo, and Gerbrand Ceder. Design principles for solid-state lithium superionic conductors. *Nature materials*, 14(10):1026–1031, 2015.
- [9] Wang Lu, Juefan Wang, Gopalakrishnan Sai Gautam, and Pieremanuele Canepa. Searching ternary oxides and chalcogenides as positive electrodes for calcium batteries. *Chemistry of Materials*, 33(14):5809–5821, 2021.
- [10] Pieremanuele Canepa, Shou-Hang Bo, Gopalakrishnan Sai Gautam, Baris Key, William D Richards, Tan Shi, Yaosen Tian, Yan Wang, Juchuan Li, and Gerbrand Ceder. High magnesium mobility in ternary spinel chalcogenides. *Nature communications*, 8(1):1759, 2017.
- [11] Clarissa Glaser, Manuel Dillenz, Kanchan Sarkar, Mohsen Sotoudeh, Zhixuan Wei, Sylvio Indris, Ruben Maile, Marcus Rohnke, Klaus Müller-Buschbaum, Axel Groß, et al. Mgb_2se_4 spinels (b= sc, y, er, tm) as potential mg-ion solid electrolytes—partial ionic conductivity and the ion migration barrier. *Advanced Energy Materials*, 14(47):2402269, 2024.
- [12] Li-Ping Wang, Zhirong Zhao-Karger, Franziska Klein, Johann Chable, Tobias Braun, Annika R Schür, Chun-Ru Wang, Yu-Guo Guo, and Maximilian Fichtner. Mgsc_2se_4 —a magnesium solid ionic conductor for all-solid-state mg batteries? *ChemSusChem*, 12(10):2286–2293, 2019.

- [13] Julius Koettgen, Christopher J Bartel, and Gerbrand Ceder. Computational investigation of chalcogenide spinel conductors for all-solid-state mg batteries. *Chemical Communications*, 56(13):1952–1955, 2020.
- [14] Felix T Böhle, Arghya Bhowmik, Tejs Vegge, Juan Maria Garcia Lastra, and Ivano E Castelli. Automatic migration path exploration for multivalent battery cathodes using geometrical descriptors. *Batteries & Supercaps*, 4(9):1516–1524, 2021.
- [15] Mohsen Sotoudeh and Axel Groß. Descriptor and scaling relations for ion mobility in crystalline solids. *JACS Au*, 2(2):463–471, 2022.
- [16] Jiayu Peng, Daniel Schwalbe-Koda, Karthik Akkiraju, Tian Xie, Livia Giordano, Yang Yu, C John Eom, Jaclyn R Lunger, Daniel J Zheng, Reshma R Rao, et al. Human-and machine-centred designs of molecules and materials for sustainability and decarbonization. *Nature Reviews Materials*, 7(12):991–1009, 2022.
- [17] Yevgen Barsukov, J Ross Macdonald, et al. Electrochemical impedance spectroscopy. *Characterization of materials*, 2:898–913, 2012.
- [18] Masayuki Itagaki, Nao Kobari, Sachiko Yotsuda, Kunihiro Watanabe, Shinichi Kinoshita, and Makoto Ue. Licoo2 electrode/electrolyte interface of li-ion rechargeable batteries investigated by in situ electrochemical impedance spectroscopy. *Journal of Power Sources*, 148:78–84, 2005.
- [19] Stephen Dongmin Kang and William C Chueh. Galvanostatic intermittent titration technique reinvented: Part i. a critical review. *Journal of The Electrochemical Society*, 168(12):120504, 2021.
- [20] Kun Tang, Xiqian Yu, Jinpeng Sun, Hong Li, and Xuejie Huang. Kinetic analysis on lifepo4 thin films by cv, gitt, and eis. *Electrochimica Acta*, 56(13):4869–4875, 2011.
- [21] Xiaoqi Sun, Patrick Bonnick, Victor Duffort, Miao Liu, Ziqin Rong, Kristin A Persson, Gerbrand Ceder, and Linda F Nazar. A high capacity thiospinel cathode for mg batteries. *Energy & Environmental Science*, 9(7):2273–2277, 2016.
- [22] Venkata Sai Avvaru, Tianyu Li, Gi-Hyeok Lee, Young-Woon Byeon, Krishna Prasad Koirala, Otavio Jovino Marques, Bernardine LD Rinkel, Yanbao Fu, David Milsted, Seonghun Jeong, et al. Alternative solid-state synthesis route for highly fluorinated disordered rock-salt cathode materials for high-energy lithium-ion batteries. *Advanced Energy Materials*, page 2500492, 2025.
- [23] Clare P Grey and Nicolas Dupré. Nmr studies of cathode materials for lithium-ion rechargeable batteries. *Chemical reviews*, 104(10):4493–4512, 2004.
- [24] VWJ Verhoeven, IM De Schepper, G Nachtegaal, APM Kentgens, EM Kelder, J Schoonman, and FM Mulder. Lithium dynamics in limn 2 o 4 probed directly by two-dimensional 7 li nmr. *Physical review letters*, 86(19):4314, 2001.
- [25] Zitan Huang, Michelle L Lehmann, Amit Bhattacharya, Yifan Liu, Valentino R Cooper, Raphaële J Clément, Tomonori Saito, Michael A Hickner, and Ralph H Colby. Enhanced anhydrous proton conductivity in azole phosphonic acid mixtures. *ACS Applied Energy Materials*, 7(23):10826–10833, 2024.

- [26] Stefan Adams. From bond valence maps to energy landscapes for mobile ions in ion-conducting solids. *Solid State Ionics*, 177(19-25):1625–1630, 2006.
- [27] Ian David Brown. Recent developments in the methods and applications of the bond valence model. *Chemical reviews*, 109(12):6858–6919, 2009.
- [28] Pierre Hohenberg and Walter Kohn. Inhomogeneous electron gas. *Physical review*, 136(3B):B864, 1964.
- [29] Walter Kohn and Lu Jeu Sham. Self-consistent equations including exchange and correlation effects. *Physical review*, 140(4A):A1133, 1965.
- [30] Hannes Jónsson, Greg Mills, and Karsten W Jacobsen. Nudged elastic band method for finding minimum energy paths of transitions. In *Classical and quantum dynamics in condensed phase simulations*, pages 385–404. World Scientific, 1998.
- [31] Graeme Henkelman, Blas P Uberuaga, and Hannes Jónsson. A climbing image nudged elastic band method for finding saddle points and minimum energy paths. *The Journal of chemical physics*, 113(22):9901–9904, 2000.
- [32] Daan Frenkel and Berend Smit. Understanding molecular simulation. *Academic Press, San Diego*, 2(2.2):2–5, 2002.
- [33] Yifei Mo, Shyue Ping Ong, and Gerbrand Ceder. First principles study of the li10gep2s12 lithium super ionic conductor material. *Chemistry of Materials*, 24(1):15–17, 2012.
- [34] Richard Car and Mark Parrinello. Unified approach for molecular dynamics and density-functional theory. *Physical review letters*, 55(22):2471, 1985.
- [35] F Meutzner, T Nestler, M Zschornak, P Canepa, GS Gautam, S Leoni, S Adams, T Leisegang, VA Blatov, and DC Meyer. Computational analysis and identification of battery materials. *Physical Sciences Reviews*, 4(1):20180044, 2019.
- [36] Tina Nestler, Stanislav Fedotov, Tilmann Leisegang, and Dirk C Meyer. Towards al3+ mobility in crystalline solids: critical review and analysis. *Critical Reviews in Solid State and Materials Sciences*, 44(4):298–323, 2019.
- [37] Xingfeng He, Yizhou Zhu, Alexander Epstein, and Yifei Mo. Statistical variances of diffusional properties from ab initio molecular dynamics simulations. *npj Computational Materials*, 4(1):18, 2018.
- [38] Volker L Deringer, Miguel A Caro, and Gábor Csányi. Machine learning interatomic potentials as emerging tools for materials science. *Advanced Materials*, 31(46):1902765, 2019.
- [39] Chi Chen and Shyue Ping Ong. A universal graph deep learning interatomic potential for the periodic table. *Nature Computational Science*, 2(11):718–728, 2022.
- [40] Xiaochen Du, James K Damewood, Jaclyn R Lunger, Reisel Millan, Bilge Yildiz, Lin Li, and Rafael Gómez-Bombarelli. Machine-learning-accelerated simulations to enable automatic surface reconstruction. *Nature Computational Science*, 3(12):1034–1044, 2023.

- [41] Reshma Devi, Baltej Singh, Pieremanuele Canepa, and Gopalakrishnan Sai Gautam. Effect of exchange-correlation functionals on the estimation of migration barriers in battery materials. *npj Computational Materials*, 8(1):160, 2022.
- [42] Søren Smidstrup, Andreas Pedersen, Kurt Stokbro, and Hannes Jónsson. Improved initial guess for minimum energy path calculations. *The Journal of chemical physics*, 140(21), 2014.
- [43] Ziqin Rong, Daniil Kitchaev, Pieremanuele Canepa, Wenxuan Huang, and Gerbrand Ceder. An efficient algorithm for finding the minimum energy path for cation migration in ionic materials. *The Journal of chemical physics*, 145(7), 2016.
- [44] Randy Jalem, Masanobu Nakayama, and Toshihiro Kasuga. An efficient rule-based screening approach for discovering fast lithium ion conductors using density functional theory and artificial neural networks. *Journal of Materials Chemistry A*, 2(3):720–734, 2014.
- [45] Randy Jalem, Kenta Kanamori, Ichiro Takeuchi, Masanobu Nakayama, Hisatsugu Yamasaki, and Toshiya Saito. Bayesian-driven first-principles calculations for accelerating exploration of fast ion conductors for rechargeable battery application. *Scientific reports*, 8(1):5845, 2018.
- [46] Austin D Sendek, Qian Yang, Ekin D Cubuk, Karel-Alexander N Duerloo, Yi Cui, and Evan J Reed. Holistic computational structure screening of more than 12000 candidates for solid lithium-ion conductor materials. *Energy & Environmental Science*, 10(1):306–320, 2017.
- [47] Anubhav Jain, Shyue Ping Ong, Geoffroy Hautier, Wei Chen, William Davidson Richards, Stephen Dacek, Shreyas Cholia, Dan Gunter, David Skinner, Gerbrand Ceder, et al. Commentary: The materials project: A materials genome approach to accelerating materials innovation. *APL materials*, 1(1), 2013.
- [48] Kwangnam Kim and Donald J Siegel. Machine learning reveals factors that control ion mobility in anti-perovskite solid electrolytes. *Journal of Materials Chemistry A*, 10(28):15169–15182, 2022.
- [49] Alexander Dunn, Qi Wang, Alex Ganose, Daniel Dopp, and Anubhav Jain. Benchmarking materials property prediction methods: the matbench test set and automatminer reference algorithm. *npj Computational Materials*, 6(1):138, 2020.
- [50] Yeonghun Kang, Hyunsoo Park, Berend Smit, and Jihan Kim. A multi-modal pre-training transformer for universal transfer learning in metal–organic frameworks. *Nature Machine Intelligence*, 5(3):309–318, 2023.
- [51] Kamal Choudhary and Brian DeCost. Atomistic line graph neural network for improved materials property predictions. *npj Computational Materials*, 7(1):185, 2021.
- [52] Reshma Devi, Keith T Butler, and Gopalakrishnan Sai Gautam. Optimal pre-train/fine-tune strategies for accurate material property predictions. *npj Computational Materials*, 10(1):300, 2024.
- [53] Reshma Devi, Avaneesh Balasubramanian, Keith T Butler, and Gopalakrishnan Sai Gautam. A literature-derived dataset of migration barriers for quantifying ionic transport in battery materials. *arXiv(2025)*.
- [54] Ilyes Batatia, Simon Batzner, Dávid Péter Kovács, Albert Musaelian, Gregor NC Simm, Ralf Drautz, Christoph Ortner, Boris Kozinsky, and Gábor Csányi. The design space of e (3)-equivariant atom-centred interatomic potentials. *Nature Machine Intelligence*, 7(1):56–67, 2025.

- [55] Ilyes Batatia, Philipp Benner, Yuan Chiang, Alin M Elena, Dávid P Kovács, Janosh Riebesell, Xavier R Advincula, Mark Asta, Matthew Avaylon, William J Baldwin, et al. A foundation model for atomistic materials chemistry. *arXiv preprint arXiv:2401.00096*, 2023.
- [56] John P Perdew, Kieron Burke, and Matthias Ernzerhof. Generalized gradient approximation made simple. *Physical review letters*, 77(18):3865, 1996.
- [57] Vladimir I Anisimov, Jan Zaanen, and Ole K Andersen. Band theory and mott insulators: Hubbard u instead of stoner i. *Physical Review B*, 44(3):943, 1991.
- [58] Jianwei Sun, Adrienn Ruzsinszky, and John P Perdew. Strongly constrained and appropriately normed semilocal density functional. *Physical review letters*, 115(3):036402, 2015.
- [59] Robert O Jones and Olle Gunnarsson. The density functional formalism, its applications and prospects. *Reviews of Modern Physics*, 61(3):689, 1989.
- [60] A Van de Walle and G Ceder. Correcting overbinding in local-density-approximation calculations. *Physical Review B*, 59(23):14992, 1999.
- [61] Mariette Hellenbrandt. The inorganic crystal structure database (icsd)—present and future. *Crystallography Reviews*, 10(1):17–22, 2004.
- [62] Iek-Heng Chu, Sayan Roychowdhury, Daehui Han, Anubhav Jain, and Shyue Ping Ong. Predicting the volumes of crystals. *Computational Materials Science*, 146:184–192, 2018.
- [63] Shyue Ping Ong, William Davidson Richards, Anubhav Jain, Geoffroy Hautier, Michael Kocher, Shreyas Cholia, Dan Gunter, Vincent L Chevrier, Kristin A Persson, and Gerbrand Ceder. Python materials genomics (pymatgen): A robust, open-source python library for materials analysis. *Computational Materials Science*, 68:314–319, 2013.
- [64] Emma Yann Zhang, Adrian David Cheok, Zhigeng Pan, Jun Cai, and Ying Yan. From turing to transformers: A comprehensive review and tutorial on the evolution and applications of generative transformer models. *Sci*, 5(4):46, 2023.
- [65] Ashish Vaswani, Noam Shazeer, Niki Parmar, Jakob Uszkoreit, Llion Jones, Aidan N Gomez, Łukasz Kaiser, and Illia Polosukhin. Attention is all you need. *Advances in neural information processing systems*, 30, 2017.
- [66] Gopalakrishnan Sai Gautam, Pieremanuele Canepa, Alexander Urban, Shou-Hang Bo, and Gerbrand Ceder. Influence of inversion on mg mobility and electrochemistry in spinels. *Chemistry of Materials*, 29(18):7918–7930, 2017.
- [67] Matthew D Witman, Anuj Goyal, Tadashi Ogitsu, Anthony H McDaniel, and Stephan Lany. Defect graph neural networks for materials discovery in high-temperature clean-energy applications. *Nature Computational Science*, 3(8):675–686, 2023.
- [68] Joseph F DeRose, Jiayao Wang, and Matthew Berger. Attention flows: Analyzing and comparing attention mechanisms in language models. *IEEE Transactions on Visualization and Computer Graphics*, 27(2):1160–1170, 2020.

- [69] Sadman Sadeed Omee, Nihang Fu, Rongzhi Dong, Ming Hu, and Jianjun Hu. Structure-based out-of-distribution (ood) materials property prediction: a benchmark study. *npj Computational Materials*, 10(1):144, 2024.
- [70] Vijay Prakash Dwivedi, Chaitanya K Joshi, Anh Tuan Luu, Thomas Laurent, Yoshua Bengio, and Xavier Bresson. Benchmarking graph neural networks. *Journal of Machine Learning Research*, 24(43):1–48, 2023.
- [71] Tian Xie and Jeffrey C Grossman. Crystal graph convolutional neural networks for an accurate and interpretable prediction of material properties. *Physical review letters*, 120(14):145301, 2018.
- [72] Alexandre Duval, Simon V Mathis, Chaitanya K Joshi, Victor Schmidt, Santiago Miret, Fragkiskos D Malliaros, Taco Cohen, Pietro Lio, Yoshua Bengio, and Michael Bronstein. A hitchhiker’s guide to geometric gnns for 3d atomic systems. *arXiv preprint arXiv:2312.07511*, 2023.
- [73] Logan Ward, Alexander Dunn, Alireza Faghaninia, Nils ER Zimmermann, Saurabh Bajaj, Qi Wang, Joseph Montoya, Jiming Chen, Kyle Bystrom, Maxwell Dylla, et al. Matminer: An open source toolkit for materials data mining. *Computational Materials Science*, 152:60–69, 2018.
- [74] Philip Sedgwick. Pearson’s correlation coefficient. *Bmj*, 345, 2012.
- [75] Ask Hjorth Larsen, Jens Jørgen Mortensen, Jakob Blomqvist, Ivano E Castelli, Rune Christensen, Marcin Dułak, Jesper Friis, Michael N Groves, Bjørk Hammer, Cory Hargus, et al. The atomic simulation environment—a python library for working with atoms. *Journal of Physics: Condensed Matter*, 29(27):273002, 2017.